

V2344®

Hot Work Tool Steel

© VILLARES METALS S/A

No part of this document may be reproduced, detached or transmitted for commercial purposes without prior written permission of the copyright holder.

VH13®, VH13SI®, VH13ISO®, TENAX300®, TENAX300IM®, VCMAIM®, VEX®, VH13IM®, VHSUPER®, VHSUPERIM®, VMO®, VPCA®, VPCAIM® and VTPLUS® are a trademarks of VILLARES METALS S/A.

The presented information in this datasheet is only for technical guidance and represents our present state of knowledge of this product. This information shall not be considered as warranty of specific properties or fitness for a particular application of this product..

Edition 1, 07.2021

V2344® – Hot Work Tool Steel

SIMILAR STANDARDS

V2344® is similar to the following grades: W.Nr 1.2344, DIN X40CrMoV5-1 and AISI H13; BS BH13; UNS T20813; JIS SKD61; AFNOR Z40CDV5; EN X40CrMoV5-1-1. This steel is produced in accordance with VDG M82.

GENERAL INFORMATION

V2344® is a 5% Cr hot work tool steel with good combination of properties such as high toughness and hot resistance. Its alloy design makes V2344® a very versatile tool steel, employed in several application in hot work tooling and plastic molds.

CHEMICAL COMPOSITION

Typical Analysis (Weight Percent)

C	Si	Mn	P	S	Cr	Mo	V	Fe
0,38	0,5	0,4	0.03 max	0.03 max	5,00	1,30	0,90	Bal.

STANDARD PRODUCTION RANGE

Production Route	Standard	Production Range	Finishing
Rolled Products	DIN 4975 VDG M82	Thickness between 8 to 152 mm with width between 38.10 to 320mm Rd. 5.50-152mm	Centerless ground Peeled Turned
Forged Products		Rd. 152 – 760 mm Thickness up to 400mm with width up to 800mm	Turned Peeled Milled

*Other dimensions and conditions are available upon inquiry.

DELIVERY CONDITION

V2344® is available in round, square or flat bars in annealed condition with maximum hardness of 235 HB. Can be supplied in hardened condition upon agreement.

MAIN CHARACTERISTICS

V2344® has a martensitic matrix mainly with fine vanadium primary carbides, and other secondary hardening carbides. Its processing ensures good isotropy and homogeneity of properties throughout the tool. In addition, V2344® presents high resistance to thermal fatigue, good machinability, polishability and high hardenability. For higher toughness applications, consider the use of VH13ISO® (NADCA Premium version) or VH13IM® (NADCA Superior version).

HEAT TREATMENTS

Soft Annealing

Soft annealing should be carried out by heat part between 840 - 860 °C for two hours controlled by the core, Cool slowly at a rate that does not exceed 20°C hour to a temperature of 650°C then air cooling. Use of protective atmosphere is important to avoid surface oxidation and decarburization.

Stress Relief

Stress relief heat treatment aims to reduce the residual stress of the part and it shall be employed after machining and before hardening. It shall be applied in dies with draws and profiles, in which the machining removal has been higher than 30%, in order to minimize distortions during and after hardening.

Stress relief heat treatment consists in a slowly heating to 650°C followed by furnace cooling until 200°C. In hardened parts, the stress relief must employ a temperature 50°C lower than the last tempering temperature.

Hardening

Preheat the part to 780- 820°C in two steps, until the temperature from center to surface is equal in each step. Austenitizing temperature should be between 1000 and 1040°C holding 30min in temperature.

For better toughness performance, it is indicated 1000°C and for better heat resistance

response 1040°C can be applied. The choice of ideal temperature should also consider aspects of design and finishing details of the parts.

After austenitization, different quenchant media are suitable:


- Pressurized vacuum furnace with pressure higher than 5 bar.
- Warm oil, 40 - 70°C.
- Salt or fluidized bed between 500 - 550°C.
- Forced air cooling.

Tempering

Temper immediately after quenching, i.e. as soon as parts reaches 60°C. Double tempering, at least is recommended and after each tempering cycle, parts shall be slowly cooled to room temperature.

Tempering temperatures are generally between 550-650°C, depending upon the desired hardness. The time of each tempering cycle shall be at least 2 hours in temperature. Avoid temperature range between 450 and 540°C as it can promote an excessive loss in toughness.

For parts with thickness larger than 70 mm, the time at temperature should be calculated according to their size, being a reference for calculation about one hour for each inch of thickness.

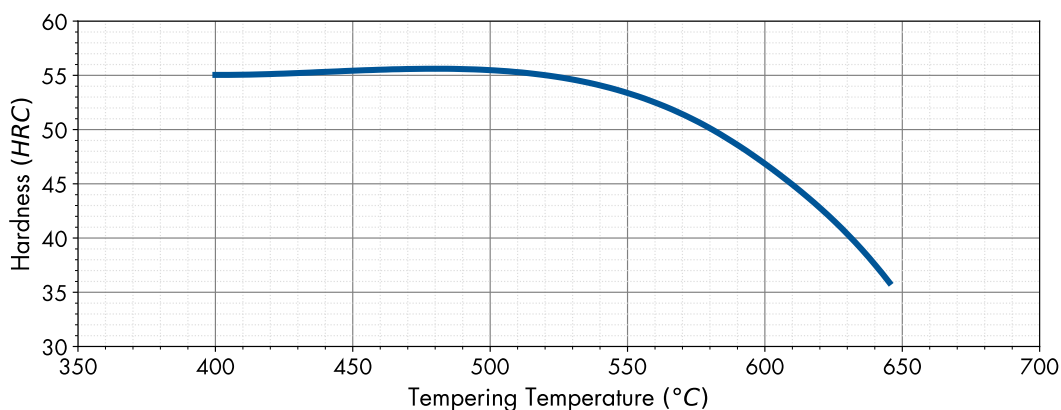

Tempering curve of V2344® after hardening at 1020°C. Tempering time: 2 hours
Curve obtained from specimens with cross section of 20 mm x 20 mm

Surface Treatments

V2344® is an adequate substrate for nitriding, leading to surface hardness around 1100 HV. Nitriding temperature should be at least 50 °C lower than that of the tempering. Surface must be in an adequate condition.

PVD or CVD coatings can also be applied in V2344® without losses in core hardness.

MAIN APPLICATIONS

The physical and mechanical properties of V2344® make possible its use in many applications, being classified as a general purpose hot work tool steel. Some typical application are presented below:

- Extrusion dies for aluminum or other non-ferrous alloys.
- Forging dies and die holders for steel or other ferrous and non-ferrous alloys.
- Hot shearing blades.
- Wear resistance parts, when nitrided.
- Injection or other molds for plastic.
- Dies for die casting of aluminum or other light metals.
- For higher performance, consider use of VH13ISO® or VH13IM®.

MACHINABILITY

V2344® can be conventionally machined in the annealed condition. Due to its refined structured, It presents good behavior in grinding operations. This contributes to reduce the risk to surface overheating and cracking. Select tools and speed carefully to allow a good machinability. In order to avoid distortions on the part during the hardening and tempering, a stress relief heat treatment before hardening stress relief is


recommended, if more than 30% of part weight in machining operations was removed. Electro-erosion process can be employed in heat treated dies or molds. After electro-erosion machining it is recommended to remove the superficial layer thru fine grinding wheel and perform a tempering heat treatment in temperatures around 50°C lower than that of the last tempering.

WELDING

It is not recommended to perform welding operations on V2344® steel. Welding operations will produce Heat Affected Zones (HAZ), which will reduce the performance of the steel in the application. HAZ produced during arc welding operation are harder and brittle, with risk of cracking unless great care is exercised. In exceptional cases and always considering that, the welding would be a temporary solution V2344® might be welded using special procedures to minimize the HAZ. The sequence of operations for repair welding depends upon its prior heat treatment. As a general guideline, it is recommended to: (a) preheat, (b) weld with appropriate filler metal, (c) perform a stress relief heat treatment, (d) machine, (e) quench and temper if in the annealed condition or stress relief if already hardened and (f) grind to final dimensions. The qualification of a specific welding procedure for repair is the key point to obtain the desired quality. The skill and experience of the welder is also a vital factor in obtaining satisfactory results.

MECHANICAL PROPERTIES

V2344® is highly resistant to softening. After 30 h at temperatures higher than 550°C, the hardness decreases only 1,0 HRC at 550°C and 9,0 HRC at 600°C.

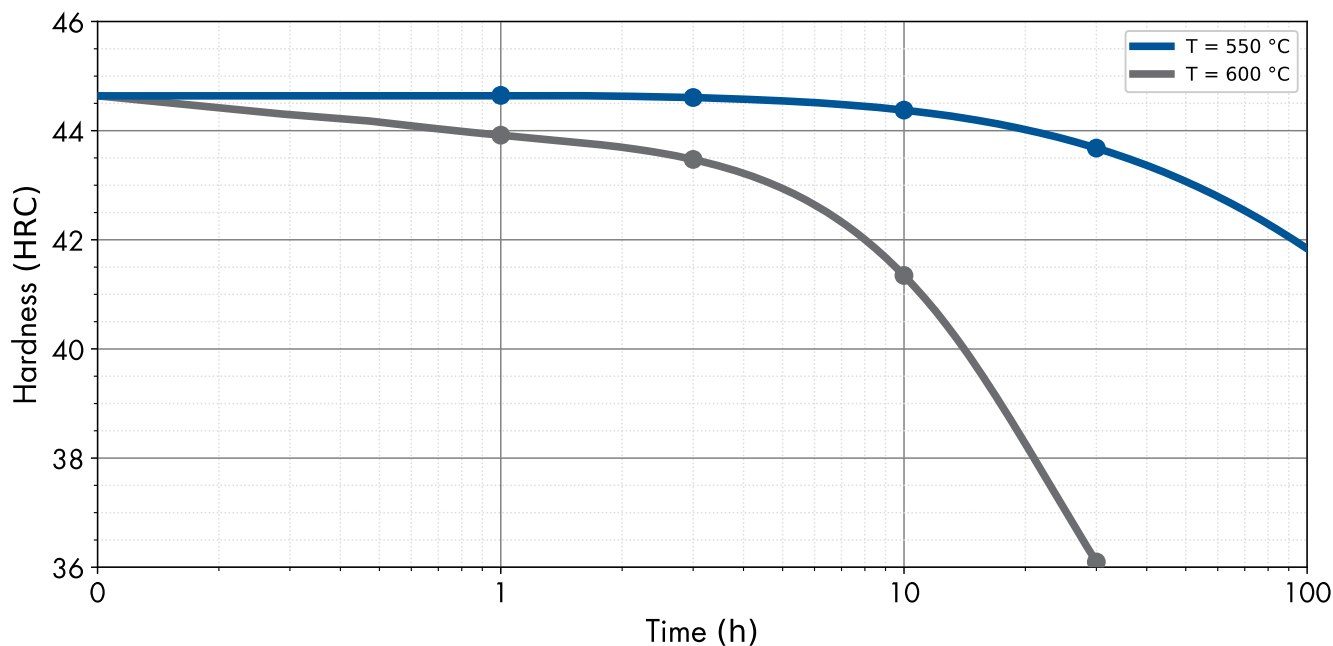

V2344® resistance to softening.
After 30 h, hardness decreases only 1,0 HRC at 550 °C and 9,0 HRC at 600 °C.

PHYSICAL PROPERTIES

Density:

Temperature	g/cm ³	lb/in ³
20°C (68°F)	7.70	0.278

Specific Heat:

Temperature 20 °C to (68°F to)	J/kg.K	Btu/lb.°F
100°C (212°F)	460	0.110

Thermal Conductivity:

Temperature	W/(m.K)	Btu.in/(h.ft ² .°F)
20°C (68°F)	25.0	173
350°C (662°F)	28.3	196
700°C (1292°F)	29.3	203

Thermal Expansion Coefficient:

Temperature 20 °C to (68°F to)	10 ⁻⁶ m/m.K	10 ⁻⁶ in/in.°F
100°C (212°F)	11.5	6.4
200°C (392°F)	12.0	6.7
300°C (572°F)	12.2	6.8
400°C (752°F)	12.5	6.9
500°C (932°F)	12.9	7.2
600°C (1112°F)	13.0	7.2

V2344® – Hot Work Tool Steel

Headquarters | Sales Office – Worldwide

Villares Metals S.A.

Rua Alfredo Dumont Villares, 155
Jardim Santa Carolina | CEP 13178.902
Sumaré - SP
+55 19 3303 8000
tooling@villaresmetals.com

Services & Solutions Centers – Brazil

Sumaré

Rua Alfredo Dumont Villares, 155
Jardim Santa Carolina | CEP 13178.902
Sumaré - SP
0800 707 0577
cac@villaresmetals.com

Joinville

Perini Business Park
Rua Dona Francisca, 8.300, bloco C7
Distrito Industrial | CEP 89219.600
Joinville - SC
0800 707 0577
cac@villaresmetals.com

Flores da Cunha

Rod VRS 814, KM 1
Lagoa Bela | CEP 95270.000
Flores da Cunha - RS
0800 707 0577
cac@villaresmetals.com

Vespasiano

Parque Norte Business Center
Avenida Três, 105
Morro Alto | CEP 33200.000
Vespasiano - MG
0800 707 0577
cac@villaresmetals.com

Sales Office – Europe

Villares Metals International B.V.

Delftse Poort - units 17.10-17.11
Weena 505
3013 AL - Rotterdam
The Netherlands
+31 6 15 95 14 51
info@villaresmetals.com



ISO 9001:2015
ISO 14001:2004 (ANAB and UKAS)
ISO 17025
ISO 50001

OHSAS 18001:2007
IATF 16949:2016
AS 9100 D
NORSOK M-650
NADCAP – Heat Treating and Non Destructive Testing

villaresmetals.com