

VWM7®

High Speed Steel

© VILLARES METALS S/A

No part of this document may be reproduced, detached or transmitted for commercial purposes without prior written permission of the copyright holder.

VWM7®, VWM2®, VWM1®, VIMAC3V®, VWM3C®, VK8E®, VKM42®, VK5E® and VHSSM50® are trademarks of VILLARES METALS S/A.

The presented information in this datasheet is only for technical guidance and represents our present state of knowledge of this product. This information shall not be considered as warranty of specific properties or fitness for a particular application of this product.

Edition 1, 02.2021

SIMILAR STANDARDS

VWM7® is similar to the following grades: AISI/SAE M7, UNS T11307, AFNOR Z100DCWV09-04-02-02, W.Nr. 1.3348, EN HS2-9-2, SHK58. This steel is produced in accord with ASTM A600 AISI M7 steel.

GENERAL INFORMATION

VWM7® is a standardized molybdenum high speed steel with a good combination of toughness and machinability coupled with a great wear resistance. The alloy design of this steel leads VWM7® to be of great versatile, suitable for various applications.

MAIN CHARACTERISTICS

VWM7® is characterized by molybdenum based chemical composition alloyed with vanadium and some tungsten. Compared to AISI M1, VWM7® higher vanadium and carbon contents result in improved abrasive wear resistance. Molybdenum and tungsten are intended to promote the precipitation of M₂C and M₆C type carbides, which promote adhesive wear resistance. Control of the carbide size results in improved toughness, promoting an excellent balance between toughness and wear resistance.

CHEMICAL COMPOSITION

Typical Analysis (Weight Percent)

C	Si	Mn	Cr	Mo	V	W	Fe
1,00	0.40	0.30	3,75	8,70	1.80	2.00	Bal.

STANDARD PRODUCTION RANGE

Production Route	Standard	Production Range	Finishing
Rolled Products	ASTM A600 AISI M7	Hot rolled coils up to 13,50 mm Drawn coils up to 12,70 mm Round bars from 0,90 to 152.40mm	As rolled Drawn Centerless ground Peeled
Forged Products		Round bars from 152.40 to 360 mm Flats with thickness up to 150mm and width up to 410mm	Peeled Turned Milled

*Other dimensions and conditions are available upon inquiry.

DELIVERY CONDITION

VWM7® is supplied in the annealed condition with a maximum hardness of 248 HB, Except for round bars up to 12 mm and drawn coils, which are supplied with a maximum hardness of 262 HB.

Identification colors: blue, gold, blue.



HEAT TREATMENTS

Soft Annealing

Soft annealing should be carried out by heating between 850 and 880°C for 2 hours, controlled from the core, followed by cooling with a cooling rate between 10 and 20°C per hour until 650°C and, then, by air cooling. The use of protective atmosphere is important to avoid surface oxidation and decarburization.

Stress Relief

Stress relief heat treatment consists in heating to 600-700°C for 2 hours minimum followed by furnace cooling until 500°C.

Hardening

Preheat the part to 400-500°C and then heat to 860-880°C until the temperature from center to surface is equal in each step. For large parts, it is also recommended an additional preheating step at 1050°C. Austenitizing temperature should be between 1160 and 1200°C for cutting tools and between 1080 and 1140°C for cold work tools. After austenitization, the quenching can be performed in different quench media as:

- Pressurized vacuum furnace with pressure higher than 5 bar,
- Salt or fluidized bed between 450 - 550°C,
- Air cooling.

Tempering

The parts shall be tempered immediately after quenching, i.e. as soon as they reach 60°C. It is necessary, at least, double tempering.

Tempering temperatures are generally between 540-600°C depending upon the desired hardness. The time of each tempering cycle shall be at least 2 hours in temperature. For parts with thickness larger than 70 mm, the time at temperature should be calculated according to their size, being a reference for calculation about one hour for each inch of thickness.


Surface treatments

Surface treatments as PVD and CVD are recommended when both abrasive and adhesive wear resistance are required. Nitriding can also be applied in order to improve abrasive wear resistance. Surface treatments shall be carried out after hardening and tempering as long as the temperature is at least 50°C lower than the last tempering heat treatment.

MAIN APPLICATIONS

VWM7® is a general purpose high speed steel which can be used in applications such as, but not limited to:

- Twist drills,
- Reamers,
- Milling cutters,
- Broaches,
- Taps,
- Dies or inserts for cold work tooling, where high wear resistance is required.

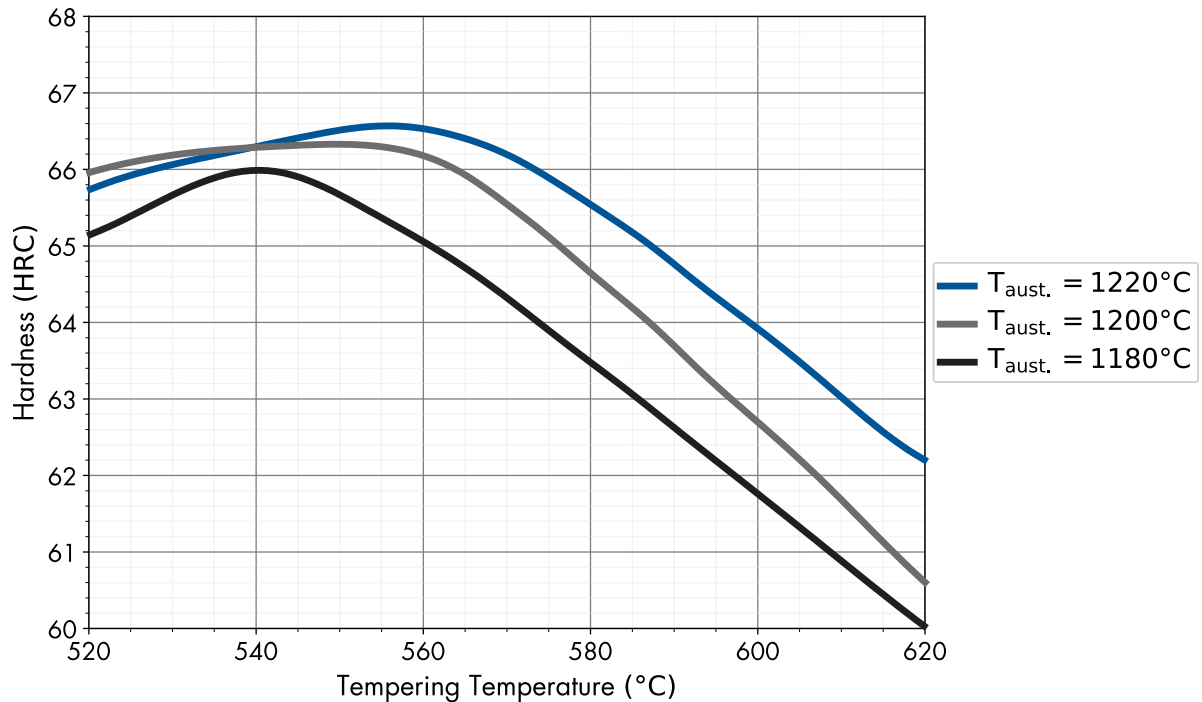

Tempering curve of VWM7® after hardening at different temperatures. Tempering time: 2 hours
Curves obtained from specimens with 20 mm x 20 mm x 20 mm

MACHINABILITY

VWM7® can be conventionally machined in the annealed condition. Care need to be taken in the selection of the tool and the speed in order to allow a good machinability and reduce the risk to surface overheating and cracking. When machining removal is greater than 30%, a stress relief is recommended as to avoid distortions on the part during the hardening and tempering, Electro-erosion process can be employed in heat treated parts. After electro-erosion machining it is recommended to remove the superficial layer thru fine grinding wheel and perform a tempering heat

treatment in temperatures around 50°C lower than that of the last tempering.

PHYSICAL PROPERTIES


Density:

Temperature	g/cm ³	lb/in ³
20°C (68°F)	7.95	0.287

Thermal Expansion Coefficient:

Temperature 20 °C to (68°F to)	10 ⁻⁶ m/m.K	10 ⁻⁶ in/in.°F
260°C (500°F)	9.5	5.3
425°C (800°F)	11,5	6.4
540°C (1000°F)	12.2	6.8
650°C (1200°F)	12,4	6.9

COMPARISON BETWEEN VILLARES METALS HIGH SPEED STEELS

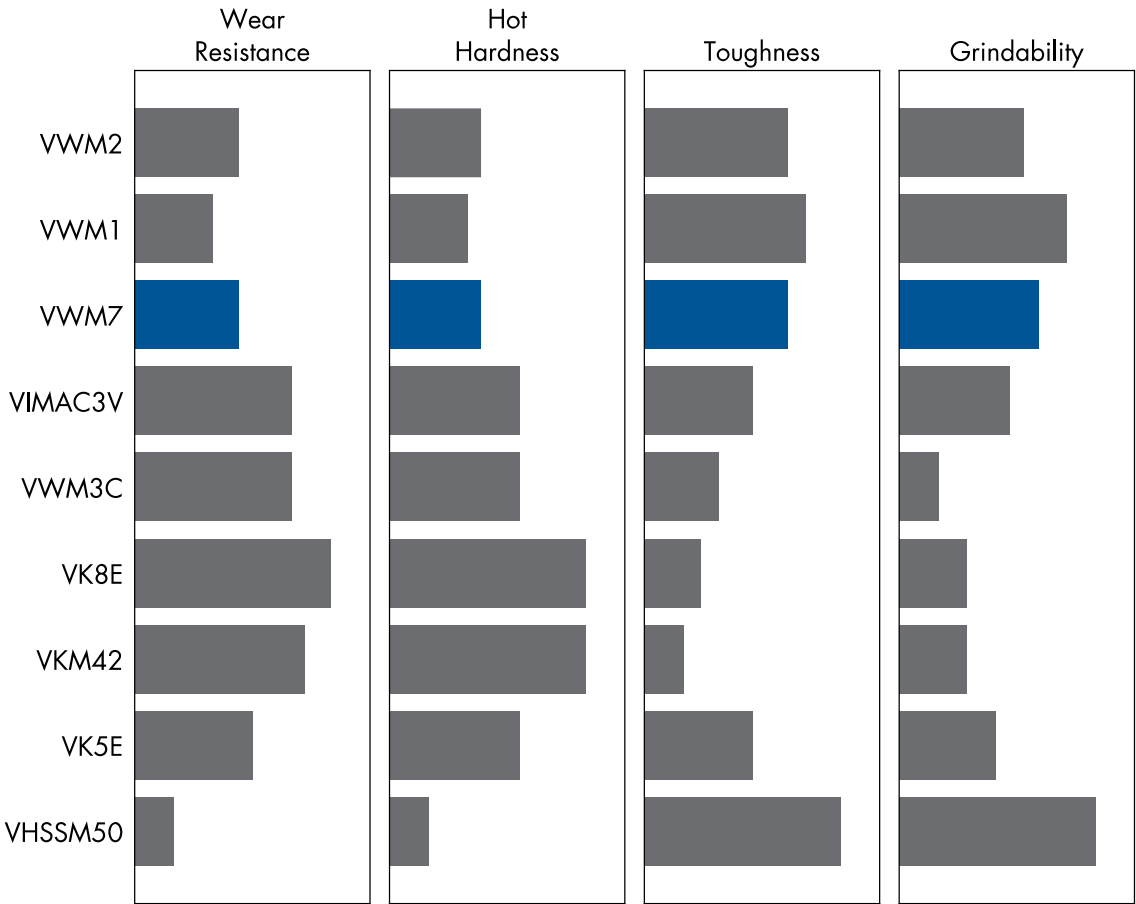

VWM7® – High Speed Steel

Headquarters | Sales Office – Worldwide

Villares Metals S.A.

Rua Alfredo Dumont Villares, 155
Jardim Santa Carolina | CEP 13178.902
Sumaré - SP
+55 19 3303 8000
tooling@villaresmetals.com

Services & Solutions Centers – Brazil

Sumaré

Rua Alfredo Dumont Villares, 155
Jardim Santa Carolina | CEP 13178.902
Sumaré - SP
0800 707 0577
cac@villaresmetals.com

Joinville

Perini Business Park
Rua Dona Francisca, 8.300, bloco C7
Distrito Industrial | CEP 89219.600
Joinville - SC
0800 707 0577
cac@villaresmetals.com

Flores da Cunha

Rod VRS 814, KM 1
Lagoa Bela | CEP 95270.000
Flores da Cunha - RS
0800 707 0577
cac@villaresmetals.com

Vespasiano

Parque Norte Business Center
Avenida Três, 105
Morro Alto | CEP 33200.000
Vespasiano - MG
0800 707 0577
cac@villaresmetals.com

Sales Office – Europe

Villares Metals International B.V.

Delftse Poort - units 17.10-17.11
Weena 505
3013 AL - Rotterdam
The Netherlands
+31 6 15 95 14 51
info@villaresmetals.com



ISO 9001:2015
ISO 14001:2004 (ANAB and UKAS)
ISO 17025
ISO 50001

OHSAS 18001:2007
IATF 16949:2016
AS 9100 D
NORSOK M-650
NADCAP – Heat Treating and Non Destructive Testing

villaresmetals.com